

Statistical analysis of time-resolved emission from ensembles of semiconductor quantum dots: interpretation of exponential decay models

A. F. van Driel,¹ I. S. Nikolaev,^{2,3} P. Vergeer,¹ P. Lodahl,^{3,4} D. Vanmaekelbergh,¹ and W. L. Vos^{2,3,*}

¹*Debye Institute, Utrecht University,*

P.O. Box 80 000, 3508 TA Utrecht, The Netherlands

²*Center for Nanophotonics, FOM Institute for Atomic and Molecular Physics (AMOLF),
1098 SJ Amsterdam, The Netherlands*

³*Complex Photonic Systems (COPS),*

*Department of Science and Technology and MESA+ Research Institute,
University of Twente, 7500 AE Enschede, The Netherlands*

⁴*COM·DTU Department of Communications, Optics, and Materials,
Nano·DTU, Technical University of Denmark, Denmark*

(Dated: Prepared for Phys. Rev. B in October, 2006.)

Abstract

We present a statistical analysis of time-resolved spontaneous emission decay curves from ensembles of emitters, such as semiconductor quantum dots, with the aim to interpret ubiquitous non-single-exponential decay. Contrary to what is widely assumed, the density of excited emitters and the intensity in an emission decay curve are not proportional, but the density is a time-integral of the intensity. The integral relation is crucial to correctly interpret non-single-exponential decay. We derive the proper normalization for both a discrete, and a continuous distribution of rates, where every decay component is multiplied with its radiative decay rate. A central result of our paper is the derivation of the emission decay curve in case that both radiative and non-radiative decays are independently distributed. In this case, the well-known emission quantum efficiency can not be expressed by a single number anymore, but it is also distributed. We derive a practical description of non-single-exponential emission decay curves in terms of a single distribution of decay rates; the resulting distribution is identified as the distribution of total decay rates weighted with the radiative rates. We apply our analysis to recent examples of colloidal quantum dot emission in suspensions and in photonic crystals, and we find that this important class of emitters is well described by a log-normal distribution of decay rates with a narrow and a broad distribution, respectively. Finally, we briefly discuss the Kohlrausch stretched-exponential model, and find that its normalization is ill-defined for emitters with a realistic quantum efficiency of less than 100 %.

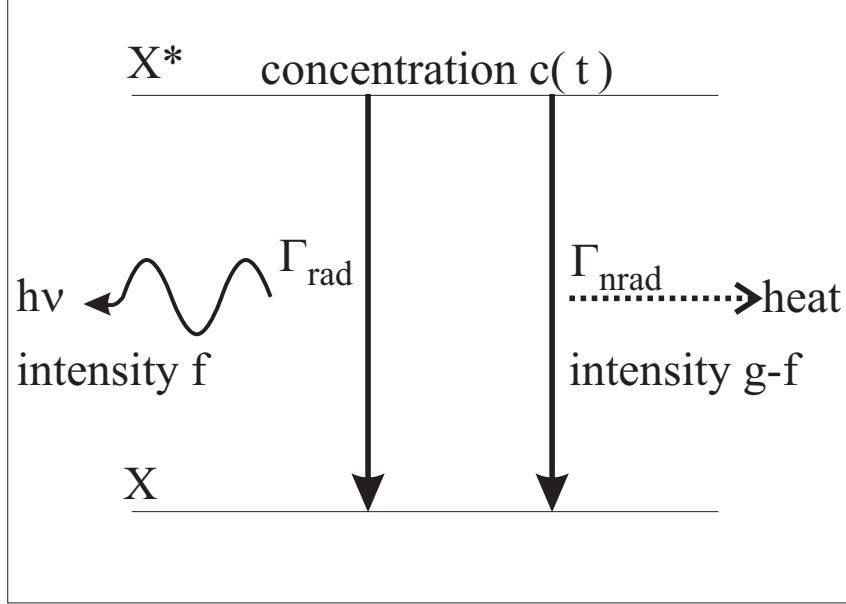


FIG. 1: Schematic of the relation between decay of an excited state X^* to the ground state X and experimental observable parameters. The density of emitters in the excited state is equal to $c(t)$ which can be probed by transient absorption. The emitted light intensity as a function of time $f(t)$ is recorded in luminescence decay measurements. In photothermal measurements the released heat $(g - f)(t)$ after photoexcitation is detected. $g(t)$ describes the total decay, i.e., the sum of the radiative and the non-radiative decay.

I. INTRODUCTION

Understanding the decay dynamics of excited states in emitters such as semiconductor quantum dots is of key importance for getting insight in many physical, chemical and biological processes. For example, in biophysics the influence of Förster resonance energy transfer on the decay dynamics of donor molecules is studied to quantify molecular dynamics^{1,2}. In cavity quantum electrodynamics, modification of the density of optical modes (DOS) is quantified by measuring the decay dynamics of light sources. According to Fermi's 'Golden Rule' the radiative decay rate is proportional to the DOS at the location of the emitter³. Nanocrystalline quantum dots^{2,4,5}, atoms^{6,7} and dye molecules^{8,9} are used as light sources in a wide variety of systems. Examples of such systems are many different kinds of photonic materials, including metallic and dielectric mirrors^{5,6,7,8,9}, cavities¹⁰, metallic films^{11,12}, two^{13,14}-, and three-dimensional¹⁵ photonic crystals.

Figure 1 shows how observable parameters are related to the decay of an excited state X^* to the ground state X . In photoluminescence lifetime measurements the decay of the number of excited emitters is probed by recording a photoluminescence decay curve ($f(t)$). The number of excited emitters $c(t)$ can be probed directly by transient absorption measurements^{16,17,18} and non-radiative decay $(g - f)(t)$ can be recorded with photothermal techniques^{19,20} (see Fig. 1). $g(t)$ is here defined as the *total* intensity, i.e., the sum of the radiative and non-radiative processes. In this paper we discuss photoluminescence lifetime measurements, which are generally recorded by time-correlated-single-photon-counting¹. The decay curve $f(t)$ consists of a histogram of the distribution of arrival times of single photons after many excitation-detection cycles¹. The histogram is modelled with a decay-function from which the decay time of the process is deduced.

In the simplest case when the system is characterized by a single decay rate Γ , the decay curve is described by a single-exponential function. However, in many cases the decay is much more complex and strongly differs from single-exponential decay^{4,15,16,21,22,23,24,25}. This usually means that the decay is characterized by a distribution of rates instead of a single rate⁴⁶. For example, ensembles of quantum dots in photonic crystals experience the spatial and orientational variations of the projected LDOS explaining the non-single-exponential character of the decay²⁶. It is a general problem to describe such relaxation processes which do not follow a simple single-exponential decay. Sometimes double- and triple-exponential models are justified on the basis of prior knowledge of the emitters¹. However, in many cases no particular multi-exponential model can be anticipated on the basis of physical knowledge of the system studied and a decision is made on basis of quality-of-fit.

Besides multi-exponential models, the stretched-exponential model or Kohlrausch function²⁷ is frequently applied. The stretched-exponential function has been applied to model diffusion processes²⁸, dielectric relaxation²⁹, capacitor discharge³⁰, optical Kerr effect experiments³¹ and luminescence decay^{32,33,34}. The physical origin of the apparent stretched-exponential decay in many processes remains a source of intense debate^{35,36,37}.

Surprisingly, in spite of the rich variety of examples where non-single-exponential decay appears, there is no profound analysis of the models available in the literature. Therefore, we present in this paper a statistical analysis of time-resolved spontaneous emission decay curves from ensembles of emitters with the aim to interpret ubiquitous non-single-exponential decay. Contrary to what is widely assumed, the density of excited emitters $c(t)$ and the intensity in

an emission decay curve ($f(t)$ or $g(t)$) are not proportional, but the density is a time-integral of the intensity. The integral relation is crucial to correctly interpret non-single-exponential decay. We derive the proper normalization for both a discrete, and a continuous distribution of rates, where every decay component is multiplied with its radiative decay rate. A central result of our paper is the derivation of the emission decay curve $f(t)$ in case that both radiative and non-radiative decays are independently distributed. In this most general case, the well-known emission quantum efficiency is also distributed. Distributed radiative decay is encountered in photonic media²⁶, while distributed non-radiative decay has been reported for colloidal quantum dots^{32,34} and powders doped with rare-earths³⁸. We derive a practical description of non-single-exponential emission decay curves in terms of the distribution of total decay rates weighted with the radiative rates. Analyzing decay curves in terms of distributions of decay rates has the advantage that information on physically interpretable rates is readily available, as opposed to previously reported analysis in terms of lifetimes. We apply our analysis to recent examples of colloidal quantum dot emission in suspensions and in photonic crystals. We find excellent agreement with a log-normal distribution of decay rates for such quantum dots. In the final Section, we discuss the Kohlrausch stretched-exponential model, and find that its normalization is ill-defined for emitters with a realistic quantum efficiency of less than 100 %.

II. DECAY MODELS

A. Relation between the concentration of emitters and the decay curve

A decay curve is the probability density of emission which is therefore modelled with a so-called probability density function³⁹. This function tends to zero in the limit $t \rightarrow \infty$. The decay of the fraction of excited emitters $\frac{c(t')}{c(0)}$ at time t' is described with a reliability function or cumulative distribution function $\left(1 - \frac{c(t')}{c(0)}\right)$ ³⁹. Here $c(0)$ is the concentration of excited emitters at $t' = 0$. The reliability function tends to one in the limit $t' \rightarrow \infty$ and to zero in the limit $t' \rightarrow 0$. The fraction of excited emitters and the decay curve, i.e., the reliability function and the probability density function³⁹, are related as follows:

$$\int_0^{t'} g(t) dt = 1 - \frac{c(t')}{c(0)} \quad (1)$$

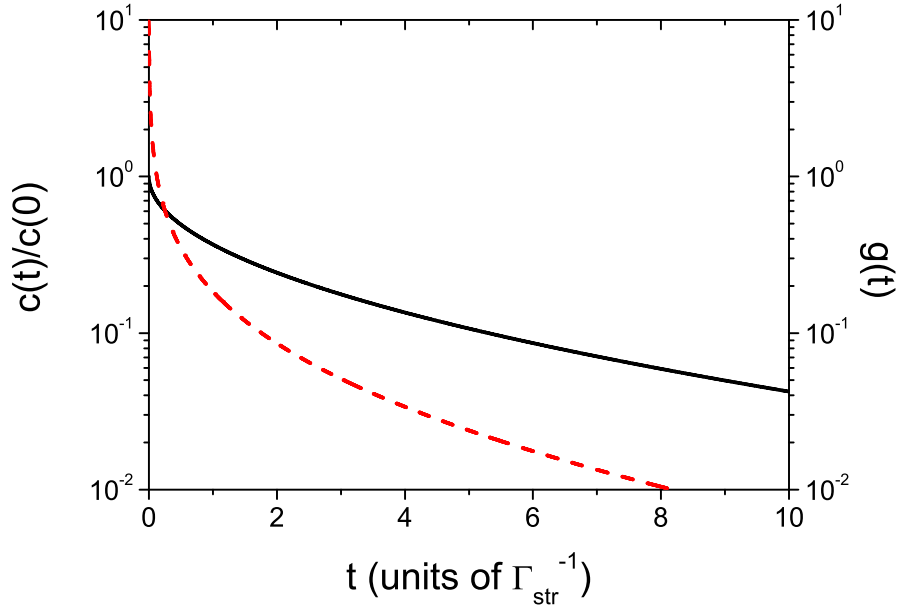


FIG. 2: (color online) Plot of a non-single-exponential decay of the fraction $\frac{c(t)}{c(0)}$ (black solid curve, left axis) and the corresponding total intensity decay curve $g(t)$ (red dashed curve, right axis). The curves that describe the fraction of excited emitters and the corresponding intensity decay curve are strongly different. In this example, $\frac{c(t)}{c(0)}$ is the Kohlrausch stretched-exponential decay of the fraction (Eq. 19, black solid curve) and $g(t)$ the corresponding decay curve (Eq. 20, red dashed curve). We have taken $\beta=0.5$ and $\Gamma_{str} = 1$.

Physically this equation means that the decrease of the concentration of excited emitters at time t' is equal to the integral of all previous decay events. Or equivalently: the total intensity $g(t)$ is proportional to the time-derivative of the fraction of excited emitters. As an illustration, Fig. 2 shows a non-single-exponential decay function simultaneously with the corresponding decay curve. It is clear that both curves are strongly different. In many reports, however, the distinction between the reliability function and the probability density function is neglected: the intensity of the decay curve $g(t)$ is taken to be directly proportional to the fraction of excited emitters $\frac{c(t')}{c(0)}$. This proportionality only holds for single-exponential decay and not for non-single-exponential decay, which has important consequences for the interpretation of non-single-exponential decay.

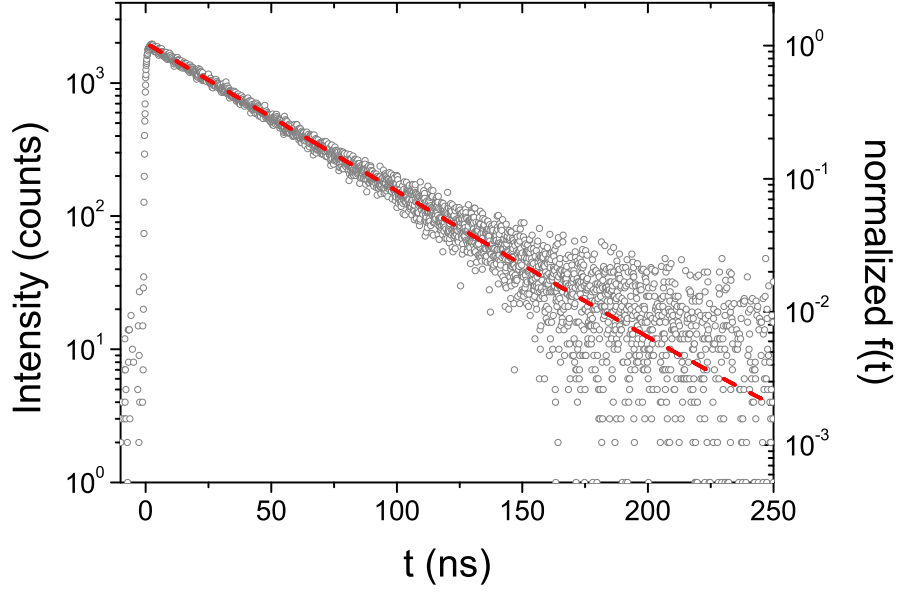


FIG. 3: (color online) Luminescence decay curve of emission from a dilute suspension of CdSe quantum dots (open dots, left axis). Data were collected at the red side of the emission maximum of the suspension, at $\lambda = 650 \pm 5 \text{ nm}$. Single-exponential modelling (red dashed curve, right axis) yields a decay time of $39.0 \pm 2.8 \text{ ns}$ and a χ_r^2 of 1.12. The average photon arrival time $\langle t \rangle$, calculated with Eq. 7, is 39.1 ns .

B. Single-exponential decay

In this section, we will illustrate some concepts with the well-known single-exponential model. We will also indicate which features of single-exponential decay will break down in the general case of non-single-exponential decay. It is well known that in case of first-order kinetics the rate of decrease of the concentration is constant in time:

$$\frac{dc(t')}{dt'} = -\Gamma c(t') \quad (2)$$

where Γ is the decay rate of the process. As a consequence, the concentration $c(t')$ decreases single-exponentially in time:

$$\frac{c(t')}{c(0)} = \exp(-\Gamma t') \quad (3)$$

The mathematical expression for the luminescence decay curve can be obtained by inserting

Eq. 3 into Eq. 1, where Γ is identified with the total decay rate Γ_{tot} , resulting in:

$$g(t) = \Gamma_{rad} \exp(-\Gamma_{tot}t) + \Gamma_{nrad} \exp(-\Gamma_{tot}t) \quad (4)$$

where Γ_{rad} is the radiative decay rate, Γ_{nrad} is the nonradiative decay rate and Γ_{tot} is the total decay rate with $\Gamma_{tot} = \Gamma_{rad} + \Gamma_{nrad}$. In a luminescence decay measurement the recorded signal is proportional to the first term of $g(t)$ only which is $f(t)$:

$$f(t) = \alpha \Gamma_{rad} \exp(-\Gamma_{tot}t) \quad (5)$$

and therefore a single-exponential luminescence decay process is modelled with Eq. 5. The pre-exponential factor α is usually taken as adjustable parameter, and it is related to several experimental parameters, i.e., the number of excitation-emission cycles in the experiment, the photon-collection efficiency and the concentration of the emitter. Henceforth α will be omitted in our analysis. A comparison between Eqs. 5 and 3 shows that in the case of pure single-exponential decay neglect of the distinction between the reliability function (Eq. 3) and the probability density function (Eq. 5) has no important consequences, since both the fraction and the decay curve are single-exponential. As Fig. 2 shows, this neglect breaks down in the case of non-single-exponential decay.

Figure 3 shows a luminescence decay curve of a dilute suspension of CdSe quantum dots in chloroform at a wavelength of $\lambda = 650 \pm 5 \text{ nm}$ ⁴⁰, with the number of counts on the ordinate and the time on the abscissa. Clearly, the data agree well with single-exponential decay as indicated by the quality-of-fit χ_r^2 of 1.12, close to the ideal value of 1. This means that all individual quantum dots that emit light in this particular wavelength-range do so with the same rate of $\frac{1}{39.0} \text{ ns}^{-1}$. It appears that the rate of emission strongly depends on the emission frequency and that it is determined by the properties of the bulk semiconductor crystal⁴⁰.

Since $f(t)$ as given by Eq. 5 is a probability density function, the probability of emission in a certain time-interval can be deduced by integration. The total probability for emission at all times between $t = 0$ and $t \rightarrow \infty$ is given by

$$\int_0^\infty f(t)dt = \int_0^\infty \Gamma_{rad} \exp(-\Gamma_{tot}t)dt = \frac{\Gamma_{rad}}{\Gamma_{tot}} \quad (6)$$

which is equal to the luminescence quantum efficiency. The luminescence quantum efficiency is defined as the probability of emission after excitation¹. The correct recovery of this result in Eq. 6 shows that Eq. 5 is properly normalized.

The average arrival time of the emitted photons or the average decay time can be calculated by taking the first moment of Eq. 5:

$$\langle t \rangle = \tau_{av} = \frac{\int_0^\infty f(t)tdt}{\int_0^\infty f(t)dt} = \frac{1}{\Gamma_{tot}} \quad (7)$$

Only in the case of single-exponential decay the average decay time $\langle t \rangle$ is equal to the inverse of the total decay rate Γ_{tot} . The average arrival time for the data in Fig. 3 was $\langle t \rangle = 39.1$ ns, very close to the value of 39.0 ± 2.8 ns obtained from single-exponential modelling, which further confirms the single-exponential character of the decay of quantum dots in suspension.

C. Discrete distribution of decay rates

In contrast to the example shown in Fig. 3, there are many cases in which decay curves cannot be modelled with a single-exponential function. As an example, Fig. 4 shows a strongly non-single-exponential decay curve of spontaneous emission from CdSe quantum dots in an inverse opal photonic crystal^{15,26}. If a non-single-exponential decay curve is modelled with a sum of single-exponentials, the decay curve has the following form:

$$f(t) = \frac{1}{c(0)} \sum_{i=1}^n c_i \Gamma_{rad,i} \exp(-\Gamma_{tot,i}t) \quad (8)$$

where n is the number of different emitters (or alternatively the number of different environments of single emitters²⁶), c_i is the concentration of emitters that has a radiative decay rate $\Gamma_{rad,i}$, and $c(0)$ is the concentration of excited emitters at $t = 0$, i.e., the sum of all concentrations c_i . When the different fractions (or environments) are distributed in a particular way, a distribution function $\rho(\Gamma_{tot})$ may be used. Such a function describes the distribution or concentration of the emitters over the emission decay rates at time $t = 0$. The fraction of emitters with a total decay rate $\Gamma_{tot,i}$ is equal to

$$\begin{aligned} \frac{c_i}{c(0)} &= \frac{1}{c(0)} \frac{(c(\Gamma_{tot,i-1}) + c(\Gamma_{tot,i+1}))}{2} \\ &= \frac{1}{2} \int_{\Gamma_{tot,i-1}}^{\Gamma_{tot,i+1}} \rho(\Gamma_{tot}) d\Gamma_{tot} \\ &= \rho(\Gamma_{tot,i}) \Delta\Gamma_{tot} \end{aligned} \quad (9)$$

where $\rho(\Gamma_{tot,i})$ expresses the distribution of the various components i over the rates $\Gamma_{tot,i}$ and has units of inverse rate s . $\Delta\Gamma_{tot}$ is the separation between the various components i in

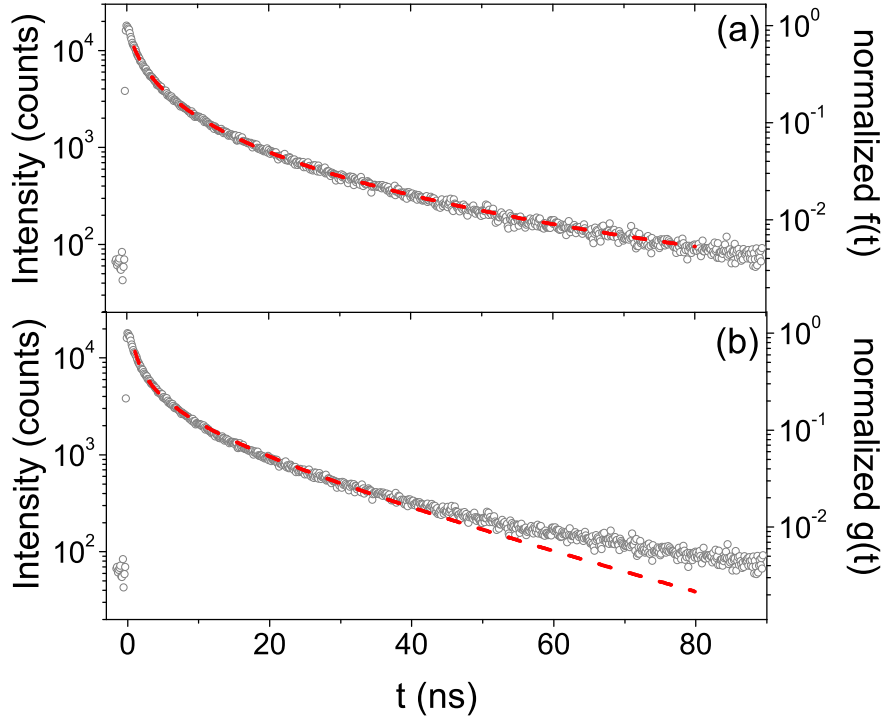


FIG. 4: (color online) Luminescence decay curve of emission from CdSe quantum dots in a titania inverse opal photonic crystal (dots, left axis). The lattice parameter of the titania inverse opal was 340 nm and the emission wavelength $\lambda = 595nm$. (a) A log-normal distribution of rates (Eq. 17 and 18, red dashed curve, right axis) models the data extremely well ($\chi_r^2=1.17$). The Γ_{mf} is $91.7 \mu s^{-1}$ ($\frac{1}{\Gamma_{mf}} = 10.9 ns$) and the width of the distribution $\Delta\Gamma$ is $0.57 ns^{-1}$. (b) In contrast, a Kohlrausch stretched-exponential model (red dashed curve, right axis) does not fit the data ($\chi_r^2 = 60.7$). The stretched-exponential curve corresponds to $\Gamma_{str}=96.2 \mu s^{-1}$ ($\frac{1}{\Gamma_{str}}=10.4 ns$), an average decay time $\langle t \rangle$ of 31.1 ns, and a β -value of 0.42.

the sum. The decay curve now has the following mathematical form:

$$f(t) = \sum_{i=1}^n \Delta\Gamma_{tot} \rho(\Gamma_{tot,i}) \Gamma_{rad,i} \exp(-\Gamma_{tot,i} t) \quad (10)$$

It is important to note that in Eq. 10 every component in the sum is correctly normalized since every component is multiplied with its radiative decay rate $\Gamma_{rad,i}$.

D. Continuous distribution of decay rates

For infinitesimal values of $\Delta\Gamma_{tot}$, Eq. 10 can be written as an integral:

$$f(t) = \int_0^\infty \Gamma_{rad}(\Gamma_{tot}) \rho(\Gamma_{tot}) \exp(-\Gamma_{tot}t) d\Gamma_{tot} \quad (11)$$

In the case of single-exponential decay the distribution function is strongly peaked around a central Γ_{tot} -value, i.e., the distribution function is a Dirac delta function. Inserting a Dirac delta function into Eq. 11 recovers Eq. 5:

$$\begin{aligned} f(t) &= \int_0^\infty \Gamma_{rad'} \delta(\Gamma_{tot} - \Gamma_{tot'}) \exp(-\Gamma_{tot}t) d\Gamma_{tot} \\ &= \Gamma_{rad'} \exp(-\Gamma_{tot'}t) \end{aligned} \quad (12)$$

This result confirms that the generalization to Eq. 11 is correct since it yields the correctly normalized single-exponential functions.

In Eq. 11 it is tacitly assumed that for every Γ_{tot} there is one Γ_{rad} : the function $\Gamma_{rad}(\Gamma_{tot})$ relates each Γ_{tot} to exactly one Γ_{rad} . In general both Γ_{tot} and Γ_{rad} vary independently, and Eq. 11 is generalized to

$$\begin{aligned} f(t) &= \int_0^\infty \left[\int_0^{\Gamma_{tot}} d\Gamma_{rad} \rho_{\Gamma_{tot}}(\Gamma_{rad}) \Gamma_{rad} \right] \rho(\Gamma_{tot}) \exp(-\Gamma_{tot}t) d\Gamma_{tot} \end{aligned} \quad (13)$$

where $\rho_{\Gamma_{tot}}(\Gamma_{rad})$ is the normalized distribution of Γ_{rad} at constant Γ_{tot} . For every Γ_{tot} the integration is performed over all radiative rates; a distribution of Γ_{rad} is taken into account for every Γ_{tot} . Eq. 13 is the most general expression of a luminescence decay curve and a central result of our paper. From this equation every decay curve with a particular distribution of rates can be recovered. An example described by Eq. 13 is an ensemble of quantum dots in a photonic crystal. In photonic crystals the local density of optical states (LDOS) varies with the location in the crystal and the distribution of dipole orientations of the emitters⁴¹. Therefore, an ensemble of emitters with a certain frequency emit light with a distribution of radiative rates Γ_{rad} . In addition, when an ensemble of emitters has a distributed Γ_{tot} and a single radiative rate Γ_{rad} , i.e., $\rho_{\Gamma_{tot}}(\Gamma_{rad})$ is a delta-function, then Eq. 13 reduces to Eq. 11. Even though the non-radiative rates may still be distributed, Eq. 11 suffices to describe the decay curve since for every Γ_{tot} there is only one Γ_{rad} . Such a situation appears, for example, with powders doped with rare earth ions³⁸ and with polymer films doped with quantum dots^{32,34}.

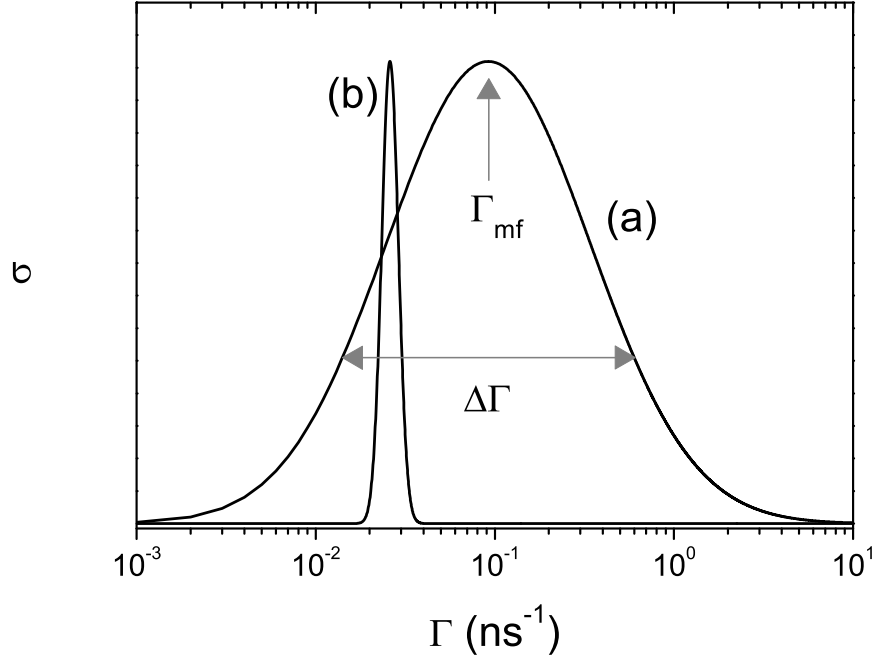


FIG. 5: Log-normal distribution of Γ . This distribution was modelled to the data of Fig. 4 (curve a, quantum dots in photonic crystal) and Fig. 3 (curve b, quantum dots in a diluted suspension), with Γ_{mf} and $\Delta\Gamma$ as adjustable parameters. For (a) Γ_{mf} is $91.7 \mu s^{-1}$ ($\frac{1}{\Gamma_{mf}} = 10.9 ns$) and the width of the distribution $\Delta\Gamma$ was $0.57 ns^{-1}$ and for (b) Γ_{mf} was $25.8 \mu s^{-1}$ ($\frac{1}{\Gamma_{mf}} = 38.8 ns$) and the width of the distribution $\Delta\Gamma$ was $0.079 ns^{-1}$.

Interestingly, an ensemble of emitters with a distribution of rates Γ_{tot} is *not* completely characterized by a single value of the quantum efficiency (as opposed to Eq. 6 for single-exponential decay). In such an ensemble, the quantum efficiency is distributed, since each Γ_{tot} is associated with a distribution of radiative rates Γ_{rad} . The average quantum efficiency $\langle QE \rangle$ can be calculated by integrating Eq. 13 for all times:

$$\begin{aligned} \langle QE \rangle &= \int_0^\infty f(t) dt \\ &= \int_0^\infty \int_0^\infty \left[\int_0^{\Gamma_{tot}} d\Gamma_{rad} \rho_{\Gamma_{tot}}(\Gamma_{rad}) \Gamma_{rad} \right] \rho(\Gamma_{tot}) \exp(-\Gamma_{tot}t) d\Gamma_{tot} dt \end{aligned} \quad (14)$$

Most often, detailed information on the relation between Γ_{tot} and Γ_{rad} is not available. Then, modelling directly with a distribution of decay rates is applied^{21,23,24,37,42}. This approach has a major advantage over modelling with a stretched-exponential function, where

it is complicated to deduce the distribution of decay rates (see below). A function of the following form is used to model the non-single-exponential decay curve:

$$f(t) = \int_0^\infty \sigma(\Gamma_{tot}) \exp(-\Gamma_{tot}t) d\Gamma_{tot} \quad (15)$$

In Eq. 15 the various components are not separately normalized as in Eq. 13. Modelling with Eq. 15 boils down to using an infinite series of single-exponentials which are expressed with only a few free parameters. The form of the distribution can usually not be predicted and a decision is made on basis of quality-of-fit. While a good fit does not prove that the chosen distribution is unique, it does extract direct physical information from the non-single-exponential decay on an ensemble of emitters and their environment²⁶.

It is widely assumed that $\sigma(\Gamma)$ is equal to the distribution of total rates^{21,23,24,43,44}. A comparison with Eq. 13 shows that this is not true and reveals that $\sigma(\Gamma)$ contains information about both the radiative and non-radiative rates:

$$\sigma(\Gamma_{tot}) = \rho(\Gamma_{tot}) \int_0^{\Gamma_{tot}} \rho_{\Gamma_{tot}}(\Gamma_{rad}) \Gamma_{rad} d\Gamma_{rad} \quad (16)$$

Thus $\sigma(\Gamma)$ is the distribution of total decay rates weighted by the radiative rates. This conclusion demonstrates the practical use of Eq. 13: the equation allows us to completely interpret the distribution of rates found by modelling with Eq. 15. Such a complete interpretation has not been reported before.

E. Log-normal distribution of decay rates

Distribution functions that can be used for $\sigma(\Gamma)$ are (sums of) normal, Lorentzian, and log-normal distribution functions. In Fig. 4(a) the luminescence decay curve of quantum dots is successfully modelled with Eq. 15, with a log-normal distribution of the rate Γ

$$\sigma(\Gamma) = A \exp \left[- \left(\frac{\ln \Gamma - \ln \Gamma_{mf}}{\gamma} \right)^2 \right] \quad (17)$$

where A is the normalization constant, Γ_{mf} is the most frequent rate constant (see Fig. 5). γ is related to the width of the distribution:

$$\Delta\Gamma = 2\Gamma_{mf} \sinh(\gamma) \quad (18)$$

where $\Delta\Gamma$ is equal to the width of the distribution at $\frac{1}{e}$. The most frequent rate constant Γ_{mf} and γ are adjustable parameters, only one extra adjustable parameter compared to a single-exponential model. Clearly, this model (Eq. 15 and 17) describes our non-single-exponential

experimental data extremely well. The χ_r^2 was 1.17, Γ_{mf} was $91.7 \mu s^{-1}$ ($\frac{1}{\Gamma_{mf}} = 10.9 ns$) and the width of the distribution $\Delta\Gamma$ was $0.57 ns^{-1}$. In addition to Γ_{mf} and $\Delta\Gamma$, an average decay rate can be deduced from the log-normal distribution in Fig. 5. However, this average is biased since the various components are weighted with their quantum efficiency, as shown in Eq. 16.

Modelling with a log-normal distribution of decay rates yields direct and clear physical parameters, for instance the shape and width of the decay rate distribution. The log-normal function is plotted in Fig. 5 (curve a). The broad distribution of rates demonstrates the strongly non-single-exponential character of the decay curve. In Ref. 26 we were able to relate the width of this broad distribution to the spatial and orientational variations of the LDOS in inverse-opal photonic crystals.

The log-normal model was also modelled to the decay curve from quantum dots in suspension (Fig. 3). The distribution is plotted in Fig. 5 (curve b). Γ_{mf} was $25.8 \mu s^{-1}$ ($\frac{1}{\Gamma_{mf}} = 38.8 ns$), close to the lifetime deduced from the single-exponential modelling of $39.0 \pm 2.8 ns$. The narrow width of the distribution $\Delta\Gamma$ of $0.079 ns^{-1}$ is in agreement with the single-exponential character of the decay curve.

F. Stretched-exponential decay

Besides the multi-exponential models discussed in Sections C-E, the Kohlrausch stretched-exponential decay model^{27,29} is widely applied to model non-single-exponential decay curves. The fraction of excited emitters, i.e., the reliability function, of the Kohlrausch stretched-exponential model is equal to:

$$\frac{c(t')}{c(0)} = \exp(-(\Gamma_{str}t')^\beta) \quad (19)$$

where β is the stretch parameter, which varies between 0 and 1, and Γ_{str} the total decay rate in case of stretched-exponential decay. The stretch parameter β qualitatively expresses the underlying distribution of rates: a small β means that the distribution of rates is broad and β close to 1 implies a narrow distribution. The recovery of the distribution of rates in case of stretched-exponential decay is mathematically complicated⁴⁷ and only feasible for specific β 's^{22,29,35,36}.

The decay curve corresponding to a Kohlrausch stretched-exponential decay of the frac-

tion $\frac{c(t')}{c(0)}$ can be deduced using Eq. 19 and Eq. 1, and results in:

$$g(t) = \frac{\beta}{t} (\Gamma_{str} t)^\beta \exp(-(\Gamma_{str} t)^\beta) \quad (20)$$

The normalization of Eq. 20 can, in analogy with Eq. 6, be deduced by integration for all times between $t = 0$ and $t \rightarrow \infty$, which yields 1. Therefore, an important consequence is that Eq. 20 is correctly normalized *only* for emitters with a quantum yield of 1 ($\Gamma_{rad} = \Gamma_{tot}$ and $f(t) = g(t)$). It is not clear how normalization should be done in realistic cases with quantum yield $< 100\%$. To the best of our knowledge, this problem has been overlooked in the literature.

The main advantage of modelling with a Kohlrausch stretched-exponential function is that the average decay time $\langle t \rangle$ can readily be calculated. The average decay time is equal to²⁹:

$$\langle t \rangle = \tau_{av} = \frac{\int_0^\infty g(t) t dt}{\int_0^\infty g(t) dt} = \frac{1}{\Gamma_{str} \beta} \bar{\Gamma}\left[\frac{1}{\beta}\right] \quad (21)$$

where $\bar{\Gamma}$ is the mathematical Gamma-function. For the single-exponential limit of $\beta \rightarrow 1$ Eq. 21 reduces to Eq. 7. Note again that in this average the various contributions are weighted with their quantum efficiency and that the average decay time $\langle t \rangle$ differs from $\frac{1}{\Gamma_{str}}$ (see Section E). Indeed, for the data in Fig. 4(b) Eq. 21 yielded an average decay time of 31.1 ns, strongly different from the $\frac{1}{\Gamma_{str}}$ -value of 10.4 ns, in contrast to the result (Eq. 5) for single-exponential decay.

It is important to note that Eq. 21 is the average decay time $\langle t \rangle$ corresponding to the decay curve given by Eq. 20. In, for instance, Refs. 32,45 the average time given by Eq. 21 has erroneously been associated to fluorescence decay described by Eq. 19.

In contrast to the single-exponential model, the reliability function and the probability density function of a stretched-exponential do *not* have the same form (see Fig. 2); the probability density function contains a time-dependent pre-factor. Therefore, the relation between the reliability function and the probability density function (Eq. 1) has important consequences. For a β -value of 0.5 the average decay time of the reliability function (Eq. 19) and of the probability density function (Eq. 20) differ by more than a factor of ten. Thus it is important to take into consideration whether Eq. 19 or Eq. 20 is used to describe the experimental photoluminescence decay curve. This is important since in many reports^{32,33,34,37,43,44}, the luminescence decay curve is modelled with the time dependence

of Eq. 19. We remark that while Eq. 19 can be used to account for the deviation from single-exponential decay, it does not represent the true Kohlrausch function, but is simply an alternative model. We argue that using the Kohlrausch stretched-exponential as a reliability function to model the fraction $\frac{c(t')}{c(0)}$ ⁴⁸ implies that the proper probability density function, i.e., Eq. 20, must be used to model a luminescence decay curve. Fig. 4(b) shows the modelling of experimental data with Eq. 20, with Γ_{str} and β as adjustable parameters. The β -value was 0.42 and Γ_{str} was $96.2 \mu s^{-1}$ ($\frac{1}{\Gamma_{str}} = 10.4 ns$). Modelling with stretched-exponential is obviously more satisfactory than single-exponential, but here fails at long times, reflected by the high χ_r^2 -value of 60.7.

III. CONCLUSIONS

We have presented a statistical analysis of time-resolved spontaneous emission decay curves from ensembles of emitters, in particular colloidal quantum dots, with the aim to interpret ubiquitous non-single-exponential decay. Contrary to what is widely assumed, the density of excited emitters $c(t)$ and the intensity in an emission decay curve ($f(t)$ or $g(t)$) are not proportional, but the density is a time-integral of the intensity. The integral relation is crucial to correctly interpret non-single-exponential decay. We have derived the proper normalization for both a discrete, and a continuous distribution of rates, where every decay component is multiplied with its radiative decay rate. A central result of our paper is the derivation of the emission decay curve $f(t)$ in case that both radiative and non-radiative decays are independently distributed (Eq. 13). In this case, the well-known emission quantum efficiency can not be expressed by a single number anymore, but it is also distributed. We derive a practical description of non-single-exponential emission decay curves in terms of a distribution of total decay rates weighted with the radiative rates. Analyzing decay curves in terms of decay rate distributions opposes to the usual and widely reported analysis in terms of distributed lifetimes. We apply our analysis to recent examples of colloidal quantum dot emission in suspensions and in photonic crystals, and we find that this important class of emitters is well described by a log-normal distribution of decay rates with a narrow and a broad distribution, respectively. Finally, we briefly discuss the Kohlrausch stretched-exponential model; we deduce the average decay time and we find that its normalization is ill-defined for emitters with a realistic quantum efficiency of less than

100 %.

IV. ACKNOWLEDGMENTS

This work is part of the research program of both the "Stichting voor Fundamenteel Onderzoek der Materie (FOM)", and "Chemische Wetenschappen", which are financially supported by the "Nederlandse Organisatie voor Wetenschappelijk Onderzoek (NWO)".

* Electronic address: w.l.vos@utwente.nl; Webpage: www.photonicbandgaps.com

- ¹ J. R. Lakowicz, *Principles of Fluorescence Spectroscopy* (Kluwer Academic/Plenum Publishers, New York, Boston, Dordrecht, London, Moscow, 1999), 2nd ed.
- ² I. L. Medintz, H. T. Uyeda, E. R. Goldman, and H. Mattoussi, *Nature Materials* **4**, 435 (2005).
- ³ R. Loudon, *The quantum theory of light*, Oxford science publications (Oxford University Press, Oxford,, 2001), 3rd ed.
- ⁴ S. A. Crooker, J. A. Hollingsworth, S. Tretiak, and V. I. Klimov, *Physical Review Letters* **89**, 186802 (2002).
- ⁵ J. Y. Zhang, X. Y. Wang, and M. Xiao, *Optics Letters* **27**, 1253 (2002).
- ⁶ K. H. Drexhage, *Journal of Luminescence* **1,2**, 693 (1970).
- ⁷ R. M. Amos and W. L. Barnes, *Physical Review B* **55**, 7249 (1997).
- ⁸ N. Danz, J. Heber, and A. Brauer, *Physical Review A* **66**, 063809 (2002).
- ⁹ S. Astilean and W. L. Barnes, *Applied Physics B-Lasers and Optics* **75**, 591 (2002).
- ¹⁰ M. Bayer, T. L. Reinecke, F. Weidner, A. Larionov, A. McDonald, and A. Forchel, *Physical Review Letters* **86**, 3168 (2001).
- ¹¹ J. S. Biteen, D. Pacifici, N. S. Lewis, and H. A. Atwater, *Nano Letters* **5**, 1768 (2005).
- ¹² J. H. Song, T. Atay, S. F. Shi, H. Urabe, and A. V. Nurmikko, *Nano Letters* **5**, 1557 (2005).
- ¹³ M. Fujita, S. Takahashi, Y. Tanaka, T. Asano, and S. Noda, *Science* **308**, 1296 (2005).
- ¹⁴ A. Kress, F. Hofbauer, N. Reinelt, M. Kaniber, H. J. Krenner, R. Meyer, G. Bohm, and J. J. Finley, *Physical Review B* **71**, 241304 (2005).
- ¹⁵ P. Lodahl, A. F. van Driel, I. S. Nikolaev, A. Irman, K. Overgaag, D. Vanmaekelbergh, and W. L. Vos, *Nature* **430**, 654 (2004).

- ¹⁶ P. Foggi, L. Pettini, I. Santa, R. Righini, and S. Califano, *Journal of Physical Chemistry* **99**, 7439 (1995).
- ¹⁷ V. I. Klimov and D. W. McBranch, *Physical Review Letters* **80**, 4028 (1998).
- ¹⁸ F. V. R. Neuwahl, P. Foggi, and R. G. Brown, *Chemical Physics Letters* **319**, 157 (2000).
- ¹⁹ A. Rosencwaig, *Photoacoustics and Photoacoustic Spectroscopy* (John Wiley & Sons, New York, 1980).
- ²⁰ M. Grinberg, A. Sikorska, and A. Sliwinski, *Physical Review B* **67**, 045114 (2003).
- ²¹ D. R. James and W. R. Ware, *Chemical Physics Letters* **126**, 7 (1986).
- ²² A. Siemiarczuk, B. D. Wagner, and W. R. Ware, *Journal of Physical Chemistry* **94**, 1661 (1990).
- ²³ J. C. Brochon, A. K. Livesey, J. Pouget, and B. Valeur, *Chemical Physics Letters* **174**, 517 (1990).
- ²⁴ J. Wlodarczyk and B. Kierdaszuk, *Biophysical Journal* **85**, 589 (2003).
- ²⁵ S. F. Wuister, A. van Houselt, C. D. M. Donega, D. Vanmaekelbergh, and A. Meijerink, *Angewandte Chemie-International Edition* **43**, 3029 (2004).
- ²⁶ I. S. Nikolaev, P. Lodahl, A. F. van Driel, and W. L. Vos, <http://arxiv.org/abs/physics/0511133> (2005).
- ²⁷ R. Kohlrausch, *Annalen der Physik* **91**, 179 (1854).
- ²⁸ L. A. Deschenes and D. A. Vanden Bout, *Science* **292**, 255 (2001).
- ²⁹ C. P. Lindsey and G. D. Patterson, *Journal of Chemical Physics* **73**, 3348 (1980).
- ³⁰ R. Kohlrausch, *Annalen der Physik* **91**, 56 (1854).
- ³¹ R. Torre, P. Bartolini, and R. Righini, *Nature* **428**, 296 (2004).
- ³² G. Schlegel, J. Bohnenberger, I. Potapova, and A. Mews, *Physical Review Letters* **88**, 137401 (2002).
- ³³ R. Chen, *Journal of Luminescence* **102**, 510 (2003).
- ³⁴ B. R. Fisher, H. J. Eisler, N. E. Stott, and M. G. Bawendi, *Journal of Physical Chemistry B* **108**, 143 (2004).
- ³⁵ D. L. Huber, *Physical Review B* **31**, 6070 (1985).
- ³⁶ F. Alvarez, A. Alegria, and J. Colmenero, *Physical Review B* **44**, 7306 (1991).
- ³⁷ M. Lee, J. Kim, J. Tang, and R. M. Hochstrasser, *Chemical Physics Letters* **359**, 412 (2002).
- ³⁸ P. Vergeer, T. J. H. Vlugt, M. H. F. Kox, M. I. den Hertog, J. van der Eerden, and A. Meijerink, *Physical Review B* **71**, 014119 (2005).

- ³⁹ E. R. Dougherty, *Probability and Statistics for the engineering, computing and physical sciences* (Prentice-Hall International, Inc., Englewood, New Jersey, 1990).
- ⁴⁰ A. F. van Driel, G. Allan, C. Delerue, P. Lodahl, W. L. Vos, and D. Vanmaekelbergh, *Physical Review Letters* **95**, 236804 (2005).
- ⁴¹ R. Sprik, B. A. van Tiggelen, and A. Lagendijk, *Europhysics Letters* **35**, 265 (1996).
- ⁴² D. R. James, Y.-S. Liu, P. De Mayo, and W. R. Ware, *Chemical Physics Letters* **120**, 460 (1985).
- ⁴³ K. C. Benny Lee, J. Siegel, S. E. D. Webb, S. Leveque-Fort, M. J. Cole, R. Jones, K. Dowling, M. J. Lever, and P. M. W. French, *Biophysical Journal* **81**, 1265 (2001).
- ⁴⁴ M. N. Berberan-Santos, E. N. Bodunov, and B. Valeur, *Chemical Physics* **315**, 171 (2005).
- ⁴⁵ J. Kalkman, H. Gersen, L. Kuipers, and A. Polman, *Physical Review B* **73**, 075317 (2006).
- ⁴⁶ In the case of strong coupling in cavity quantum electrodynamics, the decay of even a single emitter is not single-exponential. Experimental situations where this may be encountered are emitters in a high-finesse cavity, or van Hove singularities in the LDOS of a photonic crystal.
- ⁴⁷ In case of the stretched-exponential model the distribution of the rates is unknown and is generally deduced by solving the following equation^{21,32,42,43,44}: $\frac{\beta}{t}(\Gamma_{str}t)^{\beta} \exp(-(\Gamma_{str}t)^{\beta}) = \int_0^{\infty} \sigma(\Gamma) \exp(-\Gamma t) d\Gamma$ where $\sigma(\Gamma)$ is the distribution function of total decay rate weighted by Γ_{rad} . To deduce $\sigma(\Gamma)$ an inverse Laplace transform is applied. For $\beta \neq 0.5$ and $\beta \neq 1$ there is no analytical solution of this equation and therefore it is difficult to deduce the distribution function. This difficulty can be circumvented by modelling directly with a known distribution function, as is shown in this paper.
- ⁴⁸ We remark that in Refs. 27,29 capacitor discharge and dielectric relaxation are studied, which are, in contrast to a fluorescence decay curve, indeed described by a reliability function.